

# ACIERS POUR TRAVAIL À FROID

## Variantes de produits disponibles

 Produit long\*

 Tôle

\* ) Presented data refer exclusively to long products. Please observe the detailed explanations at the end of the data sheet (pdf).

## Description du produit

Outils de coupe (matrices et poinçons), outils de découpage, outils de laminage des filets, lames de cisailles.

## Procédé d'élaboration

 Airmelted

## Propriétés

- > Résistance à l'usure : très élevé
- > Résistance à la compression : très élevé
- > Stabilité dimensionnelle : bien

## Applications

- > Cisailages / couteaux pour machines
- > Découpage et emboutissage fins
- > Laminage
- > Compactage de poudre
- > Formage à froid

## Données techniques

Désignation normalisée		Normes	
1.2363	SEL	4957	EN ISO
~T30102	UNS		
X100CrMoV5	EN		
~X100CrMoV5-1			
A2	AISI		
SKD12	JIS		

## Composition chimique

C	Si	Mn	Cr	Mo	V
1,00	0,30	0,55	5,20	1,10	0,25

## Comparaison des caractéristiques

	Résistance à la compression	Stabilité dimensionnelle lors du traitement thermique	Ténacité	Résistance à l'usure abrasive
<b>BÖHLER K305</b>	★★★★★	★★★	★★	★★★★★
<b>BÖHLER K306</b>	★★★★	★★★	★★★★	★★★
<b>BÖHLER K313</b>	★★★★	★★★	★★★	★★★
<b>BÖHLER K320</b>	★★★	★★★	★★★	★★★
<b>BÖHLER K329</b>	★★★	★★★	★★★★★	★★★★★
<b>BÖHLER K600</b>	★	★★★	★★★★★	★
<b>BÖHLER K601</b>	★	★★★	★★★★★	★★
<b>BÖHLER K605</b>	★★	★★★	★★★★★	★

## Condition de livraison

### Recuit

Dureté (HB)	max. 240
-------------	----------

## Traitement thermique

### Recuit

Température	800 jusqu'à 850 °C	Slow controlled cooling in furnace at a rate of 50 to 68°F/hr (10 to 20°C/hr) down to approx. 1112°F (600°C), further cooling in air.
-------------	--------------------	---


### Recuit de détente

Température	650 °C	Slow cooling in furnace. Intended to relieve stresses set up by extensive machining, or in complex shapes. After through heating, hold in neutral atmosphere for 1 - 2 hours..
-------------	--------	--

### Trempe et revenu

Température	950 jusqu'à 980 °C	Oil, salt bath 428 to 482°F or 932 to 1022°F (220 to 250°C or 500 to 550°C), air, gas Holding time after temperature equalization: 15 to 30 minutes. After hardening, tempering to the desired working hardness, see tempering chart.
-------------	--------------------	---

### Tempering chart

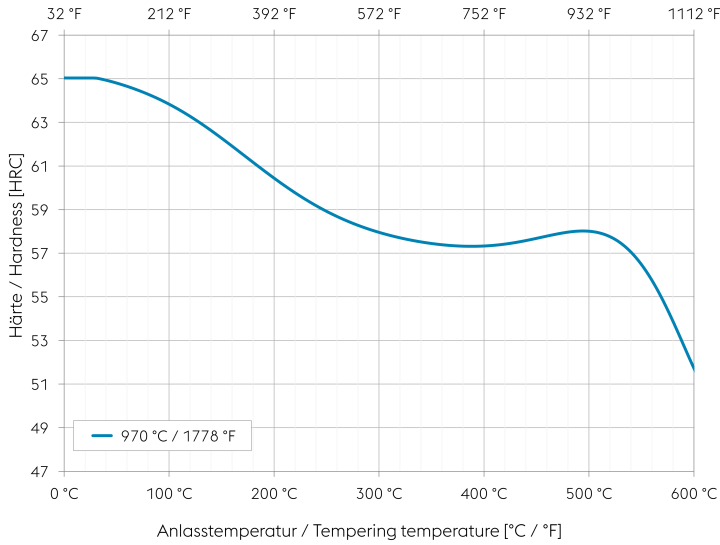

**Tempering:**

Specimen size: square 0,787 inch (20 mm)

Slow heating to tempering temperature immediately after hardening.


Time in furnace 1 hour for each 0,787 inch (20 mm) of workpiece thickness but at least 2 hours.

Slow cooling to room temperature after each tempering step is recommended.

Please refer to the tempering chart for guide values for the hardness achievable after tempering.

Tempering for stress relieving 86 to 122 °F (30 to 50 °C) below the highest tempering temperature.

### Continuous cooling CCT curves

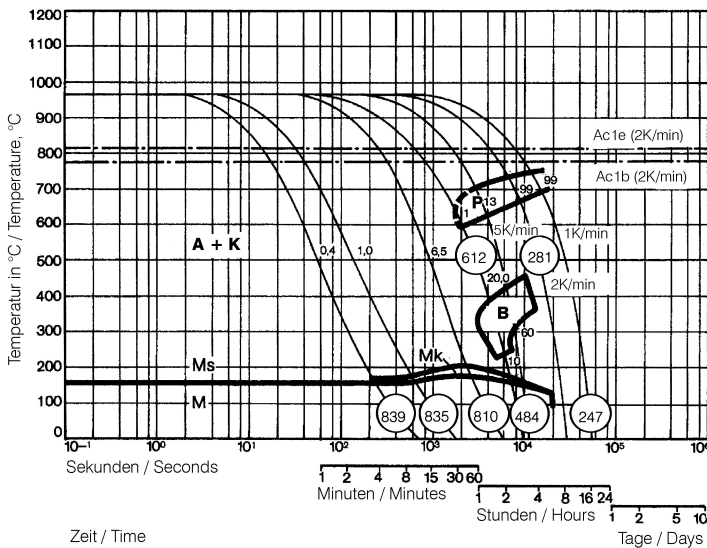

Austenitising temperature: 960°C  
Holding time: 15 minutes


O Vickers hardness

1...99 phase percentages

0.4...20.0 cooling parameter, i.e. duration of cooling from 800°C to 500°C in  $s \times 10^{-2}$

5K/min...1K/min cooling rate in K/min in the 800°C to 500°C range

**Quantitative phase diagram**

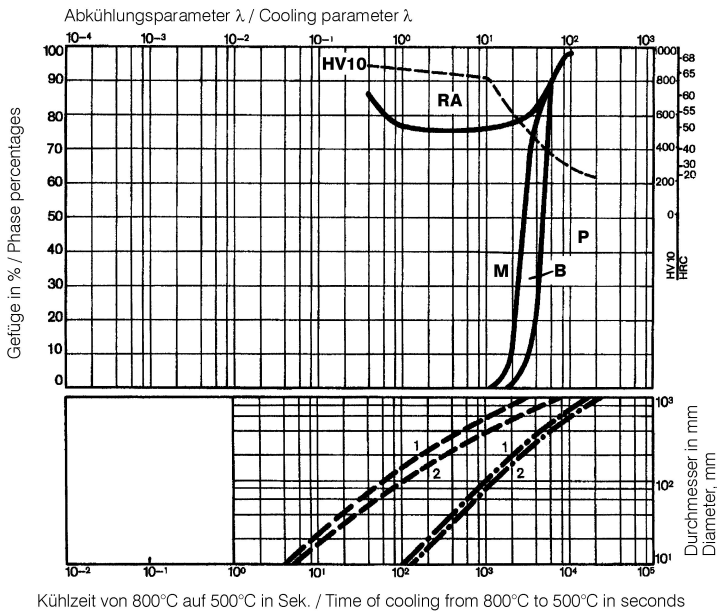


Mk... Grain boundary martensite  
 RA... Residual austenite  
 A... Austenite  
 B... Bainite  
 P... Pearlite  
 K... Carbide  
 M... Martensite

----- Oil cooling  
 - · - Air cooling

1... Edge or face  
 2... Core


**Isothermal TTT curves**

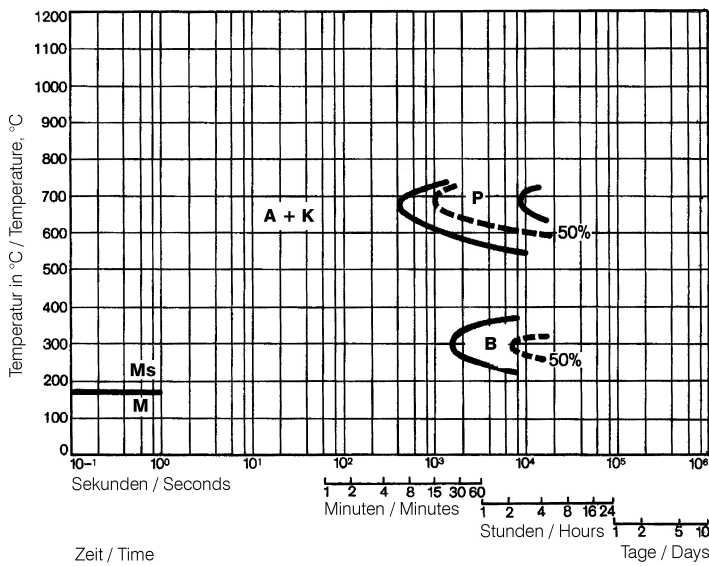


Austenitising temperature: 960°C  
 Holding time: 15 minutes

A... Austenite  
 B... Bainite  
 P... Pearlite  
 K... Carbide  
 M... Martensite

**Influence of work diameter on core hardness and hardness penetration**

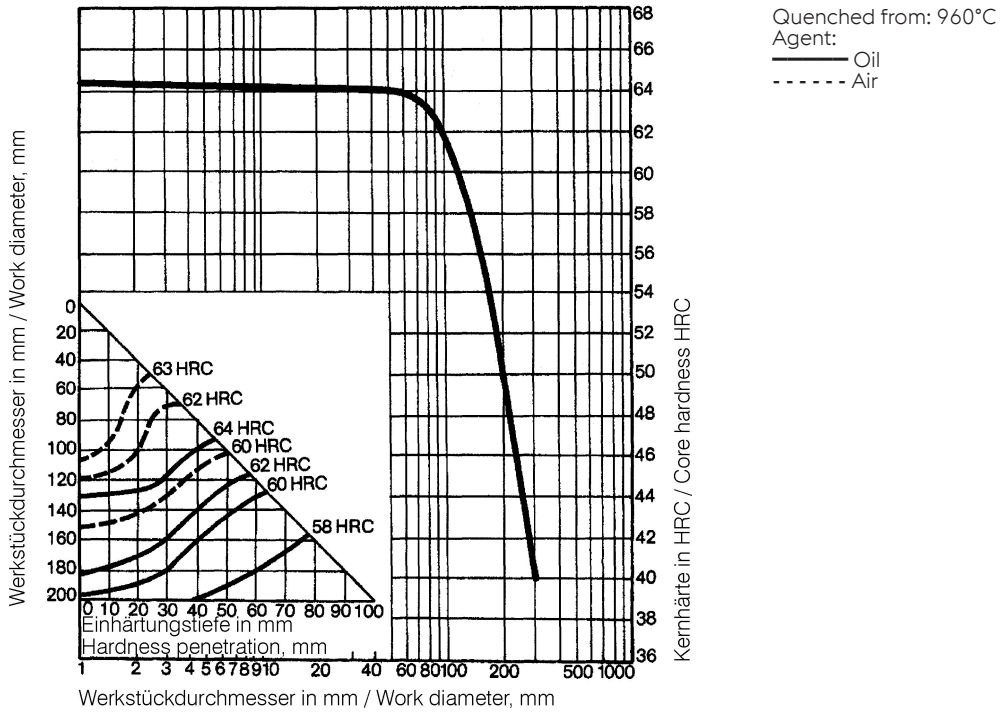

**Heat treatment sequence**

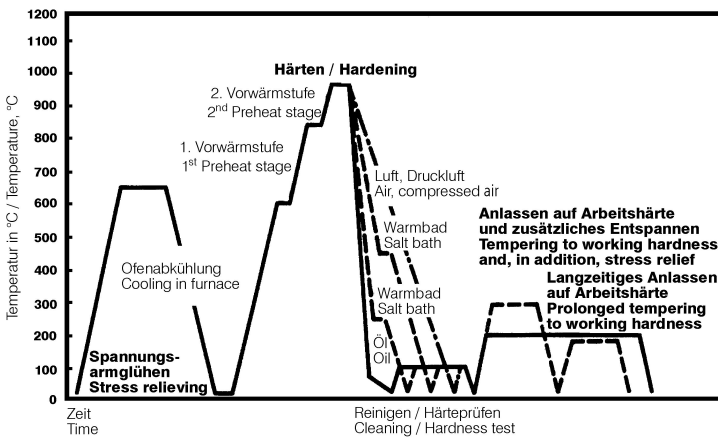

## Propriétés physiques

Température (°C)	20
Densité (kg/dm <sup>3</sup> )	7,7
Conductivité thermique (W/(m.K))	26
Chaleur spécifique (kJ/kg K)	0,46
Résistivité électrique (Ohm.mm <sup>2</sup> /m)	0,52
Module d'élasticité (10 <sup>3</sup> N/mm <sup>2</sup> )	190

## Dilatation thermique

Température (°C)	100	200	300	400	500
Dilatation thermique (10 <sup>-6</sup> m/(m.K))	12	12,1	11,9	11,6	11,7

**Long Products:** For additional specifications and technical requirements, please contact our regional voestalpine BÖHLER sales companies.

**Sheet & Plates:** Product Variant may differ in terms of melting process, technical data, delivery, and surface condition as well as available product dimensions. Please contact voestalpine BÖHLER Bleche GmbH & Co KG.

*The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.*