

# SNELDRAAISTAAL

## Beschikbare uitvoeringen

Stafstaal

## Product omschrijving

### BÖHLER S601 – "Het snelstaal"

Ideaal voor frezen, spiraalboren en schroefdraadtappen, ruimgereedschappen, koudwerkgereedschappen  
Het BÖHLER S601 is het meestgebruikte snelstaal en is het basismateriaal voor onze klanten die met snelstaal werken.

## Smeltroute

Airmeltd

## Eigenschappen

- > Taaiheid & Vervormbaarheid : hoog
- > Slijtageweerstand : hoog
- > Samenpersende sterkte : hoog
- > Randstabiliteit : hoog
- > Slijpbaarheid : hoog
- > Hete hardheid (rode hardheid) : hoog

## Toepassingen

- > Bladen voor zaagmachines
- > Koudvervorming / munten
- > Fijn stanswerk / ponsen / stampen
- > Persen van poeders
- > Walsen
- > Knippen / machinale messen
- > Slijtstukken

## Technische gegevens

Materiaal aanduiding		Normen	
1.3339	SEL	4957	EN ISO
HS6-5-2	EN	G4403	JIS
SKH51	JIS		
M2	AISI		

## Chemische samenstelling

C	Si	Mn	Cr	Mo	V	W
0,85	0,35	0,25	4,1	5	1,9	6,4

## Materiaaleigenschappen

	Drukbelastingcapaciteit	Verdraaibaarheid	Hete hardheid	Taatheid	Slijtvastheid	Behoud van snijkant
<b>BÖHLER S601</b>	★★★	★★★	★★★	★★	★★	★★★
<b>BÖHLER S200</b>	★★★	★★	★★★	★★	★★★	★★
<b>BÖHLER S400</b>	★★★	★★★	★★★	★★★	★★	★★
<b>BÖHLER S401</b>	★★	★★★	★★	★★★	★★	★★★
<b>BÖHLER S404</b>	★★	★★★	★★	★★★	★★	★★
<b>BÖHLER S430</b>	★★	★★★	★★	★★★	★★	★★
<b>BÖHLER S500</b>	★★★★	★★★	★★★★	★★	★★★	★★★
<b>BÖHLER S600</b>	★★★	★★★	★★★	★★	★★	★★★
<b>BÖHLER S607</b>	★★★	★★★	★★★	★★	★★★	★★★
<b>BÖHLER S630</b>	★★★	★★★	★★★	★★	★★	★★★
<b>BÖHLER S705</b>	★★★	★★★	★★★★	★★	★★	★★★★
<b>BÖHLER S730</b>	★★★	★★★	★★★★	★★	★★	★★★★

## Leveringsconditie

### gegloeid

Hardheid (HB)	max. 280
---------------	----------

## Warmtebehandeling

### Annealing

Temperatuur	770 naar 840 °C	Controlled slow cooling in furnace (10 - 20°C / h (50 - 68°F / h)) to approx. 600°C (1110°F), air cooling.
-------------	-----------------	--


### Stress relieving

Temperatuur	600 naar 650 °C	Slow cooling furnace.    To relieve stresses set up by extensive machining or in tools of intricate shape.    After through heating, hold in neutral atmosphere for 1 to 2 hours.
-------------	-----------------	---

### Harden en ontlaten

Temperatuur	1.190 naar 1.230 °C	Salt bath, vacuum    Preheating: 1st stage ~ 500 °C, 2nd stage ~ 850 °C, 3rd stage ~1050 °C    Austenitising: 1190 - 1230 °C, holding time after complete heating 80 seconds, maximum 150 seconds, to avoid material damage due to overheating.   Quenching: oil, warm bath (500 - 550 °C), gas
Temperatuur	550 naar 570 °C	Slow heating to tempering temperature immediately after austenitising.    Dwell time in the furnace 1 hour per 20 mm material thickness (at least 1 hour)    Slow cooling to room temperature    3 tempering cycles recommended    Hardness see tempering chart


Continuous cooling CCT curves

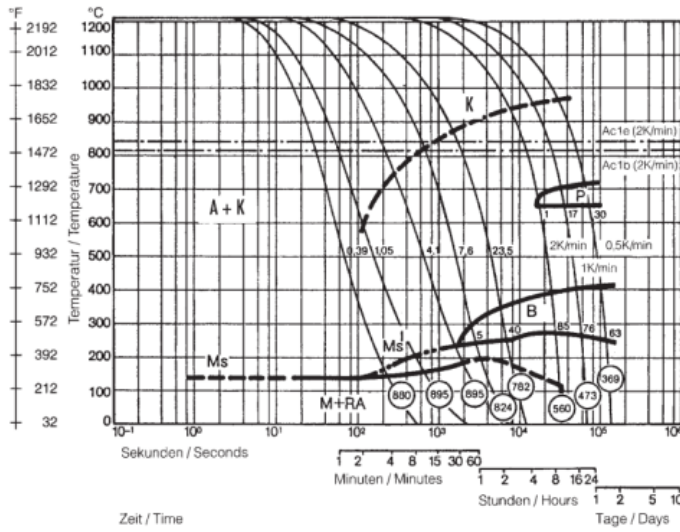

Austenitising temperature: 1210°C (2210°F)  
Holding time: 180 seconds

- A....Austenite
- B....Bainite
- K....Carbide
- P....Pearlite
- M....Martensite
- RA...Retained Austenite


Quantitative phase diagram

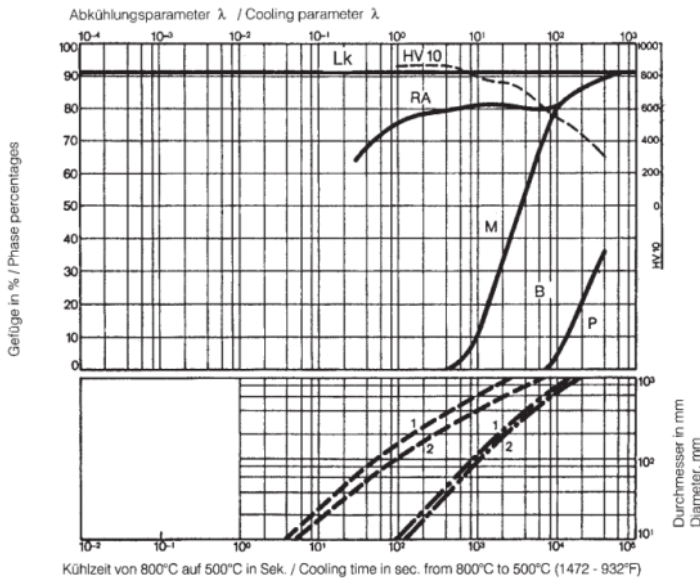

- A....Austenite
- B....Bainite
- K....Carbide
- P....Pearlite
- M....Martensite
- RA...Retained Austenite

- 1....Edge or Face
- 2....Core
- 3....Jominy test: distance from quenched end

## Tempering Chart

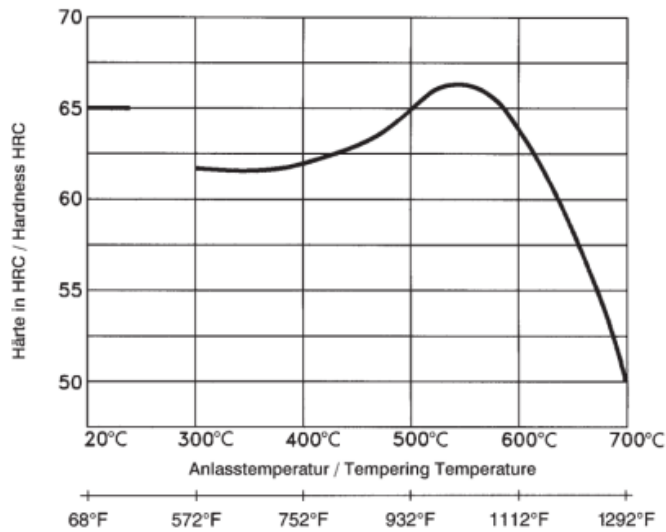

Hardening temperature: 1220°C (2228°F)

 Holding time 3 x 2 hours  
 Specimen size: square 25 mm

## Fysische eigenschappen

Temperatuur (°C)	20
Soortelijk gewicht (kg/dm <sup>3</sup> )	8,1
Thermische conductiviteit (W/(m.K))	19
Soortelijke warmte (kJ/kg K)	0,46
Specifieke elektrische weerstand (Ohm.mm <sup>2</sup> /m)	0,54
Elasticiteitsmodus (10 <sup>3</sup> N/mm <sup>2</sup> )	217

## Thermische expansie

Temperatuur (°C)	100	200	300	400	500	600	700
Thermische expansie (10 <sup>-6</sup> m/(m.K))	11,5	11,7	12,2	12,4	12,7	13	12,9

For additional specifications and technical requirements, please contact our regional voestalpine BÖHLER sales companies.

*The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.*

voestalpine BÖHLER Edelmetall GmbH & Co KG  
 Mariazeller Straße 25  
 8605 Kapfenberg, AT  
 T. +43/50304/20-0  
 E. info@boehler-edelstahl.at  
<https://www.voestalpine.com/boehler-edelstahl/de/>

ONE STEP AHEAD.